

# Chemical Recycling of Polyester Wastes *via* Catalysts Promoting Alcoholysis for Valuable Chemicals in Wood-based Structural Material Applications—A Critical Review

Jinlong Zhang,<sup>a,\*</sup> Cornelis F. De Hoop,<sup>b</sup> Qinglin Wu,<sup>b,\*</sup> and Shulin Chen<sup>c,\*</sup>

Due to the societal appeal in carbon emission reduction and neutralization, chemical recycling of waste polyester for valuable chemicals has attracted attention in an increasing number of applications. Research on chemical recycling of polyester wastes is currently rising sharply and becoming a hot spot gradually. Many technical and fundamental questions still need to be addressed, such as harsh depolymerization conditions (high temperature, long reaction time, low yields, *etc.*) and techno-economy and environmental sustainability matters. The chemical recycling protocol and optimization of degradable polyester wastes are systemically investigated along with short discussions on non-degradable ones. The thermoset polyurethane and epoxy adhesives derived from depolymerized waste polyesters for contributing to wood-based structural composite materials (*e.g.*, laminated plywood, fire retarded wood coating, and transparent wood composites) along with life-cycle assessment and techno-economic analysis are also critically evaluated and analyzed. These novel insights are expected to open a new avenue to develop wood-based structural materials *via* value-added chemicals from polyester waste recycling, which contribute to the sustainable society along with prompting further research and extension in forestry biomaterials and renewable natural resources.

DOI: 10.15376/biores.21.1.Zhang

Keywords: Waste Polyester; Chemical Recycling; Wood Composites; Transparent Wood; Wood Adhesive

Contact information: a: School for Engineering of Matter, Transport and Energy, Arizona State University, Tempe, AZ 85287, USA; b: School of Renewable Natural Resources, Louisiana State University Agricultural Center, Baton Rouge, LA 70803, USA; c: Department of Biological System Engineering, Washington State University, Pullman, WA 99164, USA; \* Corresponding authors: jinlongzhang914@gmail.com; QWu@agcenter.lsu.edu; chens@wsu.edu

## INTRODUCTION

Considering the current global plastic crisis, the annual plastic waste is projected to exceed 1 billion tons by 2060, and polyethylene terephthalate (PET) polyester waste accounts for around 12% (Li *et al.* 2025; Gao *et al.* 2025). Thus, chemical recycling of polyester waste is becoming a hot topic. Additionally, due to the societal appeal of carbon emission reduction and neutralization, the chemical recycling of polyester waste to obtain valuable chemicals in sustainable applications has attracted significant interest (Fang *et al.* 2024; Lahive *et al.* 2025). However, chemical recycling of polyester wastes currently faces many challenges, such as harsh depolymerization conditions (high temperature, long reaction time, low yields, *etc.*) and techno-economy and environmental sustainability matters (Curley *et al.* 2025; Millucci *et al.* 2025). Although a few reviews have considered

chemical recycling of *non*-degradable polyester wastes and closed-loop chemical recycling of synthetic polyester (e.g., polyethylene terephthalate PET and polycarbonate PC, etc.) via metal- and/or organo- catalysts (Enking *et al.* 2025; Jia *et al.* 2023; Luo *et al.* 2024; Zhao *et al.* 2024; Xu *et al.* 2025; Mittal *et al.* 2025), research on the degradable polyester is in its infancy (Li *et al.* 2024; Yang *et al.* 2022). This review focuses primarily on the chemical recycling of degradable polyester wastes via catalysts that enhance alcoholysis. The non-degradable polyester wastes are briefly reviewed, given the fact that the associated chemical recycling technique is relatively mature and already evaluated by pioneer scholars. Additionally, the valuable chemicals derived from waste polyester alcoholysis are ideal building blocks for synthetic thermoset resin adhesives via step growth polymerization and ring-opening polymerization, which has potential for adhesive and coating applications on the wood-based advanced structural materials as alternatives to non-environmentally friendly urea-formaldehyde and phenol-formaldehyde thermoset adhesives.

According to the Google Scholar search, only few reviews in terms of “*chemical recycling biodegradable polyester*” have been reported (Feghali *et al.* 2020; McKeown *et al.* 2020; Majgaonkar *et al.* 2021; Yang *et al.* 2022; Shi *et al.* 2024; Li *et al.* 2025). Most of these previous publications are mainly focused on the general introduction of polyester depolymerization/chemical recycling approaches, while the present review emphasizes the waste degradable polyester and chemical recycling via catalysts promoting alcoholysis. This is instead of other methods, such as hydrolysis and aminolysis or depolymerization via external stimulus (photo and electricity, etc.). Additionally, no review work has been reported on transforming the depolymerized polyester waste into valuable chemicals for wood-based structural material applications. This review will be elucidated in the following ways: Waste degradable polyesters in terms of depolymerization conditions and protocol optimizations are systemically summarized, and then different synthetic thermoset resins with building blocks derived from depolymerized waste polyesters via alcoholysis chemical recycling are discussed. Thermoset resins contributing to wood-based structural composite material applications and sustainable assessments are finally summarized in order to light the way for further research and extensions in renewable natural resources and forestry biomaterials.

## VALUABLE CHEMICALS FROM CHEMICAL RECYCLING OF POLYESTER WASTES

### Chemical Recycling of PLA Polyester Wastes

Poly(lactic acid) (PLA) has been synthesized primarily from lactic acid via ring opening polymerization. It has unique properties, such as compostability and biological compatibility, and has promising applications such as food packaging, agricultural mulch films, and biomedical materials, etc. However, its degradation completely in the natural environment requires many years (Sombatsompop *et al.* 2021). Additionally, PLA cannot degrade completely in the ocean, and these debris as microplastics and nano-plastics in seawaters threaten human health and the environment. Therefore, chemical recycling of waste PLA is needed. Compared to hydrolysis and aminolysis approaches with strong acids or bases resulting in obvious equipment corrosion (Millucci *et al.* 2025), chemical recycling of waste PLA via alcoholysis has attracted significant interest (Luo *et al.* 2024).

The general reaction mechanism of alcoholic depolymerization of PLA is explained as follows: an alkoxide as a nucleophile attacks the carbonyl group of ester backbone in the PLA and then produces valuable lactate esters or related oligomers (Odian 2007; Solomons and Fryhle 2011). The typical alcohol nucleophile in the alcoholysis of the PLA is methanol, ethanol, or ethylene glycol. Additionally, to introduce functional groups in the further polymerization (*e.g.*, ring opening metathesis and acyclic diene metathesis polymerization), modified alcohols (*e.g.*, allylic alcohol and 2-chloroethanol) are sometimes employed in PLA depolymerization (Leibfarth *et al.* 2012; Saito *et al.* 2022). The extent of the depolymerization reaction primarily depends on the strength of the nucleophiles and catalysts. Studies related to the chemical recycling of waste PLA *via* catalysts promoting alcoholysis are summarized in Table 1.

Metal catalysts are widely employed in waste PLA chemical recycling. The catalysts containing magnesium, calcium, and zinc elements usually have good catalytic effects in the alcoholysis of PLA. For instance, magnesium and calcium alkoxides were shown to catalyze alcoholysis of waste PLA under the reaction conditions of 120 to 180 °C and 1 h, and the degree of conversion reached more than 90% (Spicer *et al.* 2024). Mild depolymerization conditions along with the use of conventional yet eco-friendly synergistic or complex metal catalysts and a low-boiling solvent are highly desirable to produce ethyl lactate as a means to further optimize its depolymerization conditions. For instance, ethylene glycol as a low boiling point solvent along with various metal catalysts (*e.g.*, tetrabutyl orthotitanate, metal salt/organobase dual catalysts, and stannous octoate) has been studied relative to the alcoholysis of PLA under different reaction conditions (Majgaonkar *et al.* 2021). Alcohol and ethylene glycol as nucleophiles have some limitations. Methanol has a simple and unique structure, and it works as a strong nucleophile in the methanolysis of waste PLA, thereby inducing a decent degree of conversion. For instance, tin(II) 2-ethylhexanoate [Sn(Oct)<sub>2</sub>] with the loading at 1 wt.% catalyzed the depolymerization of PLA in methanol with conversion at more than 90% (Hofmann *et al.* 2020). However, metal catalysts have some challenges in their separation from the depolymerized lactate esters (Solomons and Fryhle 2011; Odian 2007; Hiemenz and Lodge 2007). Searching for environmentally friendly catalysts is highly desirable.

Ionic liquids and deep eutectic solvents (DESs) as benign catalysts have attracted significant interest. Ionic liquids as “melting salts” are composed of negative and positive ions. They exist in liquid form under relatively low temperature conditions. DESs as the derivatives of ionic liquids are made of compounds as hydrogen donors and accepters. Ionic liquids and DESs have good solubilization capabilities for organic substances, excellent thermal stability, and reproducibility, which are promising environmentally friendly catalysts for PLA alcoholysis. For instance, ionic liquid and/or its complex have been studied for waste PLA depolymerization, and the product conversion percentages of 85 to 90% have been reached (Liu *et al.* 2018; Hubble *et al.* 2023).  $\text{ChCl}$  and  $\text{ZnCl}_2$  as DESs catalysts have been used to recycle PLA *via* methanolysis, and the conversion reaches 98.3% at 3 h and 120 °C (Zhu *et al.* 2024). However, most ionic liquid and DESs catalysis have issues in terms of catalyst separation and recycling. To tackle these matters, organocatalysts have been used for PLA alcoholysis.

**Table 1.** Depolymerization of Waste/End-of-Life Degradable PLA via Alcoholysis

Material	Catalysts	Solvent	Time (h)	Temperature (°C)	Conversion or Yield (%)	Literature
PLA	Tetrabutyl orthotitanate	EG/PDO/BDO	1/6	240	65, 90	Nim <i>et al.</i> (2020)
PLA	Stannous octoate	EG	1	190	NA	Luo <i>et al.</i> (2024)
PLA	Zn{(R,R)-DMEG <sub>2</sub> -(1,2)ch} <sub>2</sub>	Methanol	2	60	80-90	Liu <i>et al.</i> (2024)
PLA	MHMDS	Methanol	2/60	R.T.	>90	Liu <i>et al.</i> (2024)
PLA	Titanium (IV) butoxide	PG	3	188	80-85	Figalla <i>et al.</i> (2024)
PLA	Catalyst free	Methanol	6	140	>90	Zhang <i>et al.</i> (2024)
PLA	[HTBD][OdmGly] ionic liquids	Methanol	3	70	~93	Hubble <i>et al.</i> (2023)
PLA	Zn (II) complex	Methanol	1 or 4	70-110	>94	Román-Ramírez <i>et al.</i> (2020)
PLA	Zn (HMDS) <sub>2</sub>	Methanol	2	R.T.	98	Yang <i>et al.</i> (2022)
PLA	[Ph <sub>3</sub> C][B(C <sub>6</sub> F <sub>5</sub> ) <sub>4</sub> ]	Methanol	1	120	100	Wang <i>et al.</i> (2025)
PLA	Sodium hydroxides	Methanol	1/6	30	>80	Chen <i>et al.</i> (2025)
PLA	Imidazole-anion-derived ionic liquids	Methanol	1	70	87	Liu <i>et al.</i> (2018)
PLA	Magnesium	Methanol	1	160	>90	Petrus <i>et al.</i> (2018)
PLA	Metal salt and organobase dual catalysts	EG	2	120/150/180	>90	Spicer <i>et al.</i> (2024)
PLA	Deep eutectic solvents	Methanol	3	120	>80	Zhu <i>et al.</i> (2024)

Note: ethylene glycol (EG), butane-1,4-diol (BDO), propane-1,3-diol (PDO), propylene glycol (PG) and dimethyl (or diethyl) carbonate (DMC); room temperature (R.T.); M[bis(trimethylsilyl)amide] (MHMDS, M = Li, Na, K); Mixture of N,N-dimethyl-glycine and 1,5,7-triazabicyclo[4.4.0]dec-5-ene ([HTBD][OdmGly]); Zinc bis[bis(trimethylsilyl)amide] (Zn(HMDS)<sub>2</sub>)

**Table 2.** Depolymerization of Waste Degradable PHA via Alcoholysis and Hydrolysis

Material	Catalysts	Solvent	Time (h)	Temperature (°C)	Conversion or Yield (%)	Literature
PHB	p-toluenesulfonic acid	Water	12	180	70-90	Gabirondo <i>et al.</i> (2025)
PHBV	Taurine	Water	12	180	88	Gabirondo <i>et al.</i> (2025)
PHB	Fe-containing magnetic ionic liquids	Methanol	3	110-140	70-90	Song <i>et al.</i> (2019)
PHB	[MIMPS]FeCl <sub>4</sub>	Methanol	3	140	~87	Song <i>et al.</i> (2018)
PHB	para-toluensulphonic acid	Methanol	2	151	~92	Jašek <i>et al.</i> (2022)
PHB	Acidic functionalized ionic liquids	Methanol	3	140	70-90	Song <i>et al.</i> (2016)
PHB	Ferric chloride	Methanol	1-4	130-150	70-90	Song <i>et al.</i> (2018)
PHB	Zn(HMDS) <sub>2</sub>	n-Butanol	1.5-5	70-110	>90	Wang <i>et al.</i> (2023)

Note: 1-(3-sulfonic acid)-propyl-3-methylimidazole ferric chloride ([MIMPS]FeCl<sub>4</sub>)

Organocatalysts were initially studied in catalyzed polyester synthesis *via* ring opening polymerization and depolymerization with a closed-loop approach (Saito *et al.* 2018; Deacy *et al.* 2021; Lin *et al.* 2018; Li *et al.* 2024; Chen *et al.* 2022; Yuan *et al.* 2019). Due to the good catalytic effect of organic bases or Lewis acids in controlled ring-opening polymerization of PLA synthesis, a few successful studies have been carried out on the methanolysis of PLA chemical recycling to achieve a yield at more than 90%, without catalyst separation and metal catalyst debris problems (Figalla *et al.* 2024; Xie *et al.* 2024; Wang *et al.* 2025). Therefore, organocatalysts can be regarded as the new stars in alcoholysis of PLA waste. However, most of the work has been carried out at lab scale for PLA chemical recycling. Pilot-scale chemical recycling *via* organocatalyst is highly desirable. Fortunately, diphenyl phosphate catalyzed hydrolysis of PLA has been demonstrated at the pilot scale recently (Wu *et al.* 2024). Additionally, compared to chemical recycling of single PLA waste, mixed PLA-containing waste poses huge challenges. Fortunately, the chemical recycling of mixtures has benefitted from large improvements over the most recent two years. For instance, one study achieved selective recycling as an exciting milestone currently with fast and mild depolymerization conditions (Liu *et al.* 2024).

### Chemical Recycling of PHA Polyester Wastes

As a relatively new biodegradable polymer, polyhydroxyalkanoate (PHA) has attracted attention for bioplastic and sustainable packaging along with biomedical areas (Tu *et al.* 2022). The PHA family primarily includes poly (3-hydroxyvalerate), poly(hydroxybutyrate) (PHB), and poly(hydroxybutyrate-co-valerate) (PHBV). As a primary member of PHAs, PHB homopolymer has been the most studied, as it has the potential to be synthesized within microorganisms without requiring further modification. However, PHB has inherent drawbacks as a polymer for packaging, namely brittleness and low toughness. Copolymerization of PHB with a 3-hydroxyvalerate comonomer, PHBV has been proposed to achieve better processability, higher ductility, and better impact properties. Research in terms of waste PHA recycling is still in infancy currently, and most work has focused on mechanical recycling (Dedieu *et al.* 2022; Belyamani *et al.* 2025). Chemical recycling of PHA has involved a few trials. A summary of waste PHA chemical recycling *via* alcoholysis is listed in Table 2. For instance, waste PHB chemical recycling was investigated *via* ionic liquids or their derivatives as catalysts under diverse temperature and time conditions, and the conversions were between 70 and 100%. Compared to PHB chemical recycling, as another family member of PHA, PHBV chemical recycling, has been rarely reported. One case study employed metal catalyst taurine achieved the conversion of PHBV at 88% under relative mild depolymerization conditions, *e.g.*, 180 °C and 12 h (Garbirondo *et al.* 2025). Organocatalyst as an environmentally friendly catalyst is highly desirable in PHA chemical recycling as it has been extensively employed in catalyzed synthesis of PHA recently (Saito *et al.* 2018; Deacy *et al.* 2021). However, almost no research has been reported on the organocatalyzed waste PHA chemical recycling.

Polybutylene adipate terephthalate (PBAT), polybutylene succinates (PBS), and polycaprolactone (PCL) as other common degradable polymers have applications widely such as shopping bags, packaging sheets, agricultural films, and biomedical materials. Table 3 lists methods for the chemical recycling of these degradable polyesters.

**Table 3.** Depolymerization of Other Waste Degradable Polyesters *via* Alcoholysis and Hydrolysis

Material	Catalyst	Solvent	Time (h)	Temperature (°C)	Conversion or Yield (%)	Literature
PBAT	Adipic acid	Water	8	170	~75	Zheng <i>et al.</i> (2024)
PBAT	Tin-based catalysts	Methanol	7	140	30-50	Parodi <i>et al.</i> (2023)
PBS	Succinic acid	Water	5	150	100	Zheng <i>et al.</i> (2024)
PCL	Zn(OAc) <sub>2</sub>	Methanol	10	160	40-80	Cheung <i>et al.</i> (2021)
PCL	TBD	Methanol	1-3	80	>90	Dong <i>et al.</i> (2022)

Note: 1,5,7-triazabicyclo [4,4,0] dec-5-ene (TBD)

**Table 4.** Depolymerization of Waste/End-of-Life PET and PC *via* Alcoholysis

Material	Catalyst	Solvent	Time (h)	Temperature (°C)	Conversion or Yield (%)	Literature
PET	Antimony (III) oxide or Zinc acetate	EG	1/12-5/12	240	>90	Mohammadi <i>et al.</i> (2020)
PET	CaCO <sub>3</sub> /CaO/TiO <sub>2</sub>	EG	1.5	200	~95	Enayati <i>et al.</i> (2024)
PET	Organocatalyst Et <sub>3</sub> N	Methanol	2	200	88	Muangmeesri <i>et al.</i> (2024)
PET	TBD	EG	1/4	100	>90	Olazabal <i>et al.</i> (2024)
PET	Amino acid-based cholinium ionic liquids	EG	6	150	51	Marullo <i>et al.</i> (2021)
PC	DBU/DMAP	EG	24	80	>95	Edge <i>et al.</i> (2025)

Note: Calcium carbonate (CaCO<sub>3</sub>), calcium oxide (CaO), and titanium dioxide (TiO<sub>2</sub>); 1,8-diazabicyclo [5.4.0] undec-7-ene (DBU) and 4-(dimethyl amino) pyridine (DMAP) *via* continuous flow conditions

As it is widely used in agricultural films, PBAT chemical recycling has been intensively studied recently. For example, water as the hydrolysis solvent has been carried out, due to its capability of achieving depolymerization under relatively high temperature (Zheng *et al.* 2024). Tin-based catalysts with methanolysis depolymerization of PBAT were further explored for its depolymerization in relatively mild conditions (Parodi *et al.* 2023).

A few studies have examined PBS chemical recycling. However, it was carried out with harsh alkali solutions, and the conversion was not satisfactory. The yield was slightly more than 50% with long time at 48 h (Zheng *et al.* 2024). Future studies should investigate PBS chemical recycling with advanced catalyst approaches. Alternatively, waste PCL depolymerization with organocatalyst 1,5,7-triazabicyclo 4.4.0 dec-5-ene (TBD) *via* methanolysis has been studied with relatively mild conditions (Dong *et al.* 2022). Organocatalyst is an environmentally friendly, economic and promising approach for PCL waste chemical recycling compared to the metal catalyst, enhancing its methanolysis (Cheung *et al.* 2021). Such an approach can possibly be applied for the depolymerization of waste polyglycolic acid, another degradable polyester, which is not widely focused on currently. Chemical recycling of non-degradable polyester waste is another important task currently.

### Chemical Recycling of Non-Degradable Polyester Wastes

PET is the most widely used polyester, and it is used in such plastic items as bottles and fabrics. As PET is not degradable in nature (de Carvalho *et al.* 2025), its chemical recycling research was initialized early compared to degradable PLA, PBAT, and PHA. As the research on chemical recycling of PET waste is relatively mature, this review primarily discusses typical cases. For more studies, please refer to a recent review paper (Tan *et al.* 2025). Herein, the typical technology in terms of its chemical recycling *via* alcoholysis is introduced shortly in Table 4. For example, the PET alcoholysis under metal catalyst was initially studied under harsh conditions, *e.g.*, 240 °C, for which its conversion is great, at almost 100% (Mohammadi *et al.* 2020). The chemical recycling at relatively mild conditions (15 min and 100 °C) *via* organocatalyst was also carried out, and the conversion could reach more than 90% (Olazabal *et al.* 2024). In another chemical recycling trial with Net3 catalyst under methanolysis, the conversion reached 90% (Muangmeesri *et al.* 2024).

As another non-degradable polyester, polycarbonate (PC) is an important engineering plastic. With unique properties, such as robust mechanical properties and excellent thermal resistance, PC is widely used in many fields, such as automotives and aerospace. Chemical recycling of these end-of-life PC materials has also been studied (Qin *et al.* 2024; Wu *et al.* 2025). However, the alcoholysis of waste PC chemical recycling approach is relatively new (Padhi *et al.* 2024; Edge *et al.* 2025), and there is a need for future studies.


### SYNTHETIC THERMOSET RESINS FOR ADHESIVES AND FUNCTIONAL COATING BY UPCYCLING MONOMERS, OLIGOMERS, OR MACROMOLECULES OF POLYESTER WASTES AND LIGNIN EXTRACTED FROM WOOD

Chemical recycling offers opportunities to upcycle waste polyesters into valuable monomers and oligomers or macromolecules (Gupta *et al.* 2025). These valuable products derived from chemical recycling of waste polyesters are unique raw materials for thermoset

synthesis toward wood adhesive and coating applications. As a suitable end-of-life solution, this approach decreases the dependence on raw petroleum-based materials for producing thermosets, polyurethane, polyurea, epoxy and cross-linked polyacrylic resins.

### Conventional Polyurethane/Polyurea Resins

Polyurethane and polyurea have excellent flexible and outstanding chemical resistance, which are the prevalent choices in adhesives and coating applications (Senra *et al.* 2023). Polyurethane or polyurea is usually synthesized *via* polyols or polyamine and diisocyanates with or without catalyst. It sounds like a sustainable approach to the synthetic polyurethane from polyols *via* chemical recycling of waste PET. However, few studies of synthetic polyurethane and polyurea with chemical recycling of waste polyesters have been carried out, as the waste polyester chemical recycling is in its infancy. As a typical case, the polyols were prepared *via* the oligo-esters by waste PET glycolysis and aromatic/aliphatic diacids and then reacted with diisocyanates to produce polyurethane (Pu *et al.* 2024). As another example, a one-step conversion of bisphenol A-based polycarbonate to produce valuable-added diols with varying chain lengths was investigated. The resulting polyols were subsequently utilized as soft segments in combination with 4,4'-methylene diphenyl diisocyanate in the production of polyurethanes as potential for wood adhesive applications in Fig. 1 (Godinho *et al.* 2021; Saito *et al.* 2025).

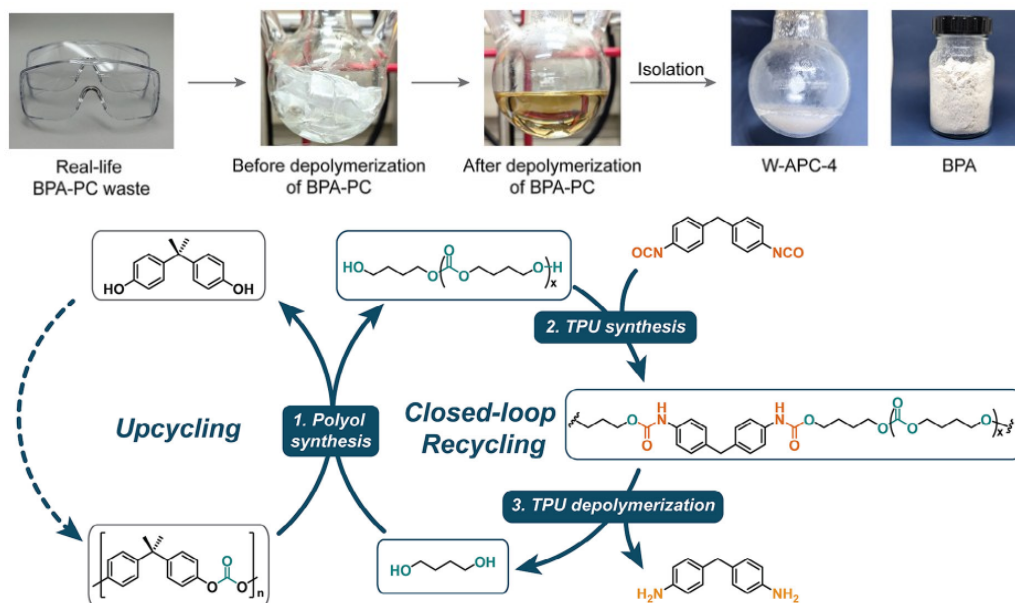

**Fig. 1.** PC alcoholysis chemical recycling and utilization of recycled valuable chemicals in synthetic polyurethanes (Saito *et al.* 2025). Figure republished with permission from Wiley Publishing Co.

### Conventional Epoxy Resins

As another classical thermoset for adhesive and coating applications, epoxy is usually prepared by a diamine curing agent and prepolymer *via* the condensation polymerization of bisphenol A and epichlorohydrin. Due to their excellent adhesive strength and thermal stability, recycled PET derived chemicals are ideal building blocks to produce epoxy resins for coating and adhesive applications. For instance,  $\alpha$ ,  $\omega$ -dicarboxylic acid oligo (ethylene succinate-co-terephthalate) and terephthalic acid as the valuable added oligomer and small molecule were produced from the chemical recycling of waste PET

and then worked as the curing agent to prepare epoxy resins (Hoang *et al.* 2022). Currently, research on waste PLA and PHA chemical recycling for epoxy resin synthesis is rare, as the chemical recycling technology of waste PLA and PHA degradable polyesters are at their early stages (Liu *et al.* 2024; Luo *et al.* 2024; Yang *et al.* 2022; Lehnertz *et al.* 2022). However, the upcycling value-added products from waste PLA and PHA contributing to epoxy and PU resin synthesis will be continuously increasing (Nim *et al.* 2023; Cheng *et al.* 2025).

### Dynamic Covalent Crosslinked Epoxy and PU Resins

Compared to the conventional covalent cross-linked epoxy and PU resin adhesives, development of dynamic covalent cross-linked epoxy and PU vitrimer resins as reworkable adhesives and coatings in wood-based structural material are promising to deal with their end-of-life challenges. For instance, PET waste was upcycled to produce closed-loop recyclable vitrimer plastics. To be more specific, catalyst- and solvent-free chemical recycling provided a direct approach to deconstruct PET waste into vitrimer building blocks from mixed PET sources. The readily available Jeffamine T403 was used for the depolymerization of PET waste to form a nucleophilic, tetraamine macromonomer, and then reacted with diacetoacetates to form dynamic covalent vinylogous urethane linkages. The resulting vitrimer materials exhibited closed-loop chemical recyclability (Danielson *et al.* 2025). This work opens a new avenue to design dynamic covalent bonded thermosets from chemical recycling of waste polyesters, such as PLA and PHA. As another example, oligomers depolymerized from PET *via* glycerol alcoholysis were studied for the preparation of vitrimer materials (Wei *et al.* 2023). In addition to using valuable chemicals from chemical recycling of polyester, the renewable natural sources derived from wood products (*e.g.*, lignin) are desirable for building blocks in the synthetic PU and epoxy vitrimer resins (Saito *et al.* 2022; Comí *et al.* 2025; Sun *et al.* 2025). Such resins have potential for wood adhesives.


## WOOD-BASED ADVANCED STRUCTURAL MATERIALS VIA UPCYCLING CHEMICALS DERIVED ADHESIVES AND COATINGS

### Adhesive in Lumbers, Plywood, and Particle Boards

Wood-based structural materials have wide applications in North America, such as construction (wooden structures, beams, and walls) and indoor furniture products (tables, chairs, wardrobes, and bookcases). According to the data from 2020 to 2022, North America utilized wood-based structure materials at a volumetric rate of over 20 million m<sup>3</sup>/year (Garcia *et al.* 2024). Lumber is primarily produced as a solid product sawn from logs, while plywood and oriented strand board are two major types of wood-based structural materials made of adhesive-bonded wood veneers and wood fibers/flakes, as shown in Fig. 2.

Over two-thirds of the manufacturing process of wooden products require adhesives to form strong chemical bonds between wood fibers, ensuring that the wood is connected stably and securely at the adhesive joints for enhancing the overall performance and adding value to wooden products (Gonçalves *et al.* 2021). Thermosetting resin phenol-formaldehyde synthetic *via* condensation polymerization of phenol and formaldehyde using acid or base catalyst are the most used wood adhesives along with urea-formaldehyde and melamine-formaldehyde thermoset resins due to their low-cost and strong bond

strength performance in both dry and wet environmental conditions (Oadian *et al.* 2007). However, these thermosets tend to release formaldehyde and other harmful gases, posing a risk to human health (Wang *et al.* 2017; Bansode *et al.* 2021). The development of environmentally friendly formaldehyde-free adhesives is attracting attention. Renewable resources-based wood adhesives attracted extensive studies, such as, cellulose, lignin or soy protein adhesives (Huzyan *et al.* 2021; Neitzel *et al.* 2023; Ghahri *et al.* 2025). However, the development of environmentally friendly adhesives at the cost of intrinsic bond strengths in conventional thermoset adhesives can't meet the requirements for real wood construction application due to the potential safety considerations (Wang *et al.* 2020; Peng *et al.* 2023; Chen *et al.* 2024). Epoxy and polyurethane or polyurea thermosets are ideal alternatives to urea-formaldehyde and phenol-formaldehyde as wooden adhesives, as they have comparative mechanical properties without toxic gas release issues. Additionally, it is a feasible strategy to preserve the advantages of conventional thermoset wood adhesives and introduce the new building units in conventionally synthetic epoxy and polyurethane or polyurea resins by borrowing value-added chemicals from chemical recycling of waste polyesters. This approach can make sense, given the current energy shortage crisis and growing environmental awareness of people. For instance, the diols from glycolysis waste PET can be used as polyols, chain extenders of PU synthesis (Pu *et al.* 2024).

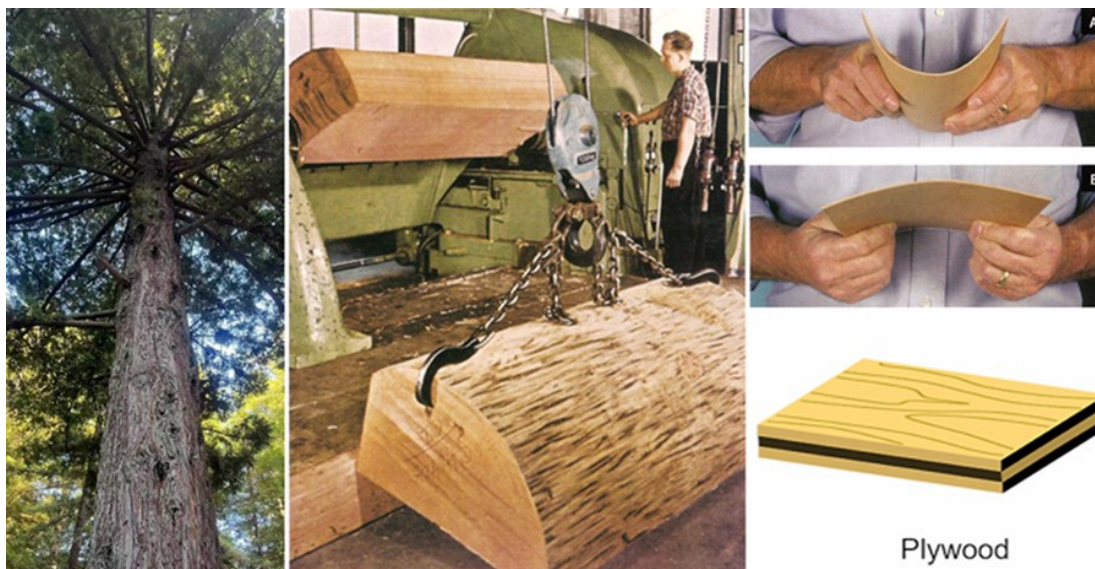


**Fig. 2.** Wood veneers were cut from timber and plywood produced from wood veneers via hot press (Hoadley 2000; Chen *et al.* 2024). Figure republished with permission from Hoadley (2000); Copyright 2024, American Chemical Society

**Table 5.** Environmentally Friendly PU and Epoxy-based Wood Adhesives from Waste Polyester Depolymerization

Adhesives	Wet SS (MPa)	Dry SS (MPa)	Test Standard	Literature
PUU	NA	10.9	DINEN302-1	Thoma <i>et al.</i> (2024)
PU	NA	1.6	ASTM D1002	Pu <i>et al.</i> (2024)
PU	7.4	11.7	ASTM D 2339-98	Phetphaisit <i>et al.</i> (2013)
Epoxy	1.7	1.8	ANSI/HPVA HP-1-2000	Mousavi <i>et al.</i> (2019)

Note: Shear strength, SS; poly(urethane urea) (PUU)

However, the research on PU or epoxy resins from chemical recycling of waste polyesters for wood adhesives is still in its infancy. For instance, the synthesis approach involved an NCO-terminated prepolymer formed by polypropylene glycol and isophorone diisocyanate followed by introducing recycling PET for a chain extension reaction to rapid cross-linking and expansion of PU chain segments (Pu *et al.* 2024). The PU adhesives synthetic from chemical recycling of waste polyesters are listed in Table 5. For instance, the PU adhesives were prepared from hydroxyl liquid natural rubbers and modified chemical recycled PET. It is worth noting that the glycolysis of PET waste was used as the chain extension for PU synthesis (Phetphaisit *et al.* 2013). Waterborne polyurethane provides an option for wooden adhesives, besides conventional PU. As the primary chemical constitutes conventional waterborne polyurethane formulations, the synthesis of CO<sub>2</sub>-based polyols *via* CO<sub>2</sub> and propylene oxide copolymerization offers a dual carbon management strategy in addition to toxic isocyanate chemical alternatives. For instance, the lignin-based waterborne polyurethane adhesive exhibited superior bonding performance, and this adhesive also demonstrated closed-loop recyclability *via* ethanol dissolution (Li *et al.* 2025). In addition to PU adhesives, epoxy and polyacrylic-based adhesives work for wood-based composites. For instance, epoxy resins made of bisphenol A diglycidyl ether, polyamidoamine, and polyethylenimine were studied as plywood adhesives (Mousavi *et al.* 2019). To replace toxic BPA in environmentally friendly adhesives for wood, lignin is an ideal alternative in epoxy adhesives for future studies. Except for PU and epoxy adhesives, hydroxyl-functional polyacrylic polymers cross-linked by the polysilazane have been investigated as wood adhesives (Chatterjee *et al.* 2025).

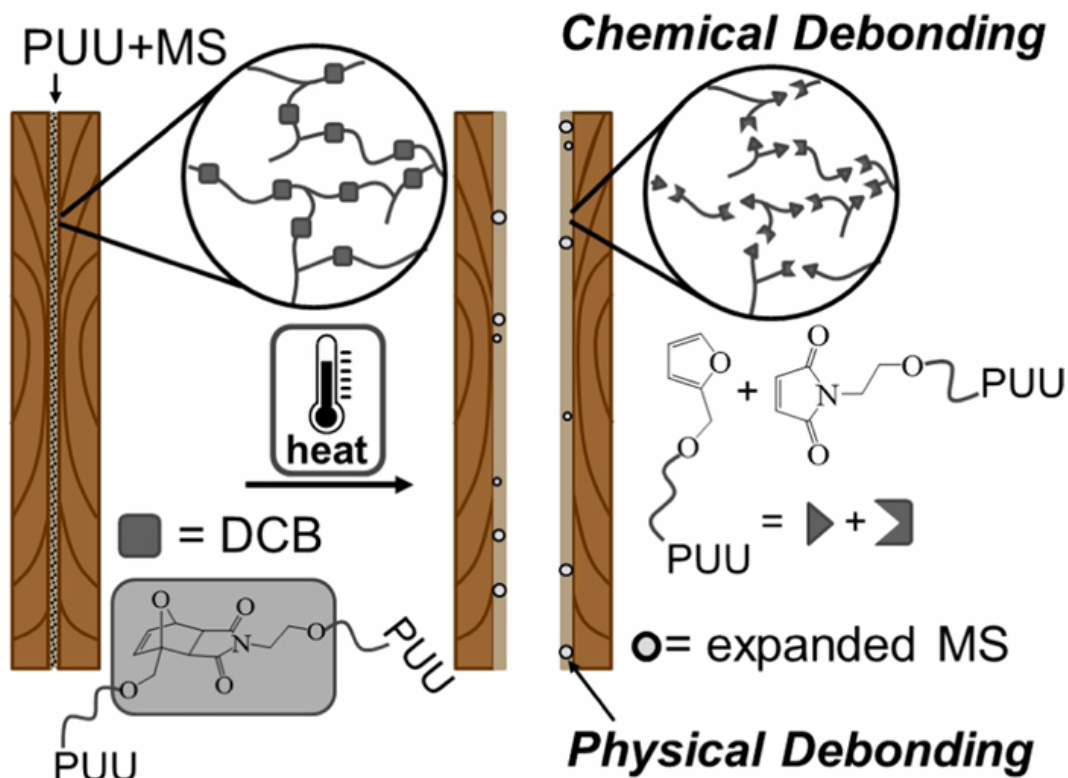


**Fig. 3.** Dynamic covalent bonded synthetic PUU as reworkable and recyclable wood adhesives (Thoma *et al.* 2024). Copyright 2024, American Chemical Society, CC-BY 4.0.

However, conventional thermosets with covalently chemical bonding adhesion are difficult to restore when the bonding interface is damaged or fractured, which reduces the service life of wooden products (Lian *et al.* 2025; Thoma *et al.* 2024). The thermoset adhesives with dynamic covalent bonds to replace the default covalent bonds make it possible to address the dilemma in dealing with end-of-life wooden products, such as poly(urethane urea) adhesives with dynamic covalent bonds of furan and maleimide in Fig. 3 (Thoma *et al.* 2024). For instance, a thermoplastic hyperbranched polyurethane adhesive with a polyurethane prepolymer and lipoic acid with S-S bonds as the terminal groups were designed as wood adhesive with the ability to bond repeatedly. Under heating conditions, the dynamic exchange of S-S bonds occurs on both sides of the damaged interface, leading to reformation of the polymer network structure on both sides of the break and restoration of the adhesive strength (Zhou *et al.* 2025).

### Functional Coating in Fire Retardancy and Moisture Stability along with Early Fire Alarm Warning of Lumbers, Plywood, and Particle Boards

Wood-based structural materials have fire retardancy and moisture stability issues, which restrict their broad applications (Gašparik *et al.* 2017; Hosseinashrafi *et al.* 2023). Especially, enhancing fire retardancy of wood-based structural composites is a long-term and tough question. The conventional way is by infusing fire additive particles into wood substrates. However, this approach has its intrinsic issues. Fire resistance often is achieved at the cost of other properties, such as mechanical properties. As an alternative approach, fire retarding wood-based structural materials can be achieved *via* surface coating of epoxy or PU; such an approach has been used to design fire retarding wood composites (Jin *et al.* 2017; Wang *et al.* 2017; Jang *et al.* 2025). In addition to the fire retarding matter, moisture stability is another practical matter of wood-based composites.

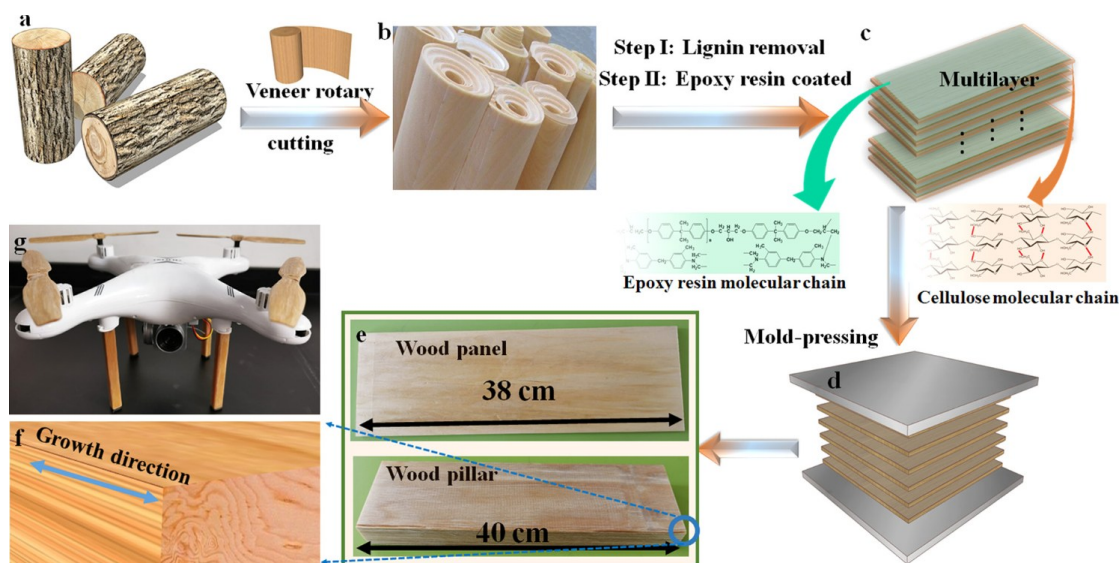


**Fig. 4.** Laminated wood composites from delignified wood veneers (Tang *et al.* 2021). Figure republished with permission from American Chemical Society.

Waterborne polyurethane based fire-resistant, and waterproof coating has been synthesized for wood protection (Hao *et al.* 2023). Polyacrylic based copolymer resin doped with organo-clays coating has been developed for plywood protection (Chuang *et al.* 2011). Additionally, epoxy resins have potential as coating on wood substrates as a

means to extend their life-times, as indicated in Fig. 4. For instance, lignin-derived epoxy resin coating has been developed for wood fire retarding protection (Liang *et al.* 2025). As another case, bio-based epoxy resin derived from phytic acid and itaconic acid as coating has been studied as fire retarding protection of rubber wood (Li *et al.* 2022; Zhang *et al.* 2025; Zuo *et al.* 2025). Except for basic wood protection, the surface coating wood-based structural materials has potential to fulfill safety protection functions such as fire alarm warning sensors (Fan *et al.* 2025). However, the research on waste polyester derived epoxy resin wood adhesives has a few studies, and it is highly desirable for further research in the future.

### Transparent Wood-based Composites

Transparent wood has gained attention recently. Owing to its unique merits, such as high optical transmittance and efficient mechanical and thermal insulation properties, transparent wood has potential for applications such as windows, ceiling, and rooftops as alternatives to plate glass in Fig. 5 (Jia *et al.* 2019; Popović *et al.* 2022; Yang *et al.* 2024). To prepare delignified transparent wood-based composites from wood veneers, wood veneers are immersed in 1 wt.% sodium chlorite under controlled reaction conditions, pH (pH 4.6) and temperature (80 °C). Next, resins with similar refractive index, *e.g.*, epoxy resin and poly(methyl methacrylate) (PMMA), are impregnated into bleached wood pores *via* vacuum (Yue *et al.* 2021; Cheng *et al.* 2022). Epoxy resins with both optical and adhesive properties are useful in the design of transparent wood-based structural composites. For instance, transparent wood was prepared *via* the bleaching process by KOH and NaClO<sub>2</sub> treatment to remove the hemicellulose and lignin effectively, and the resulting pores in woods were impregnated with epoxy resin for transparent wood composites (Cai *et al.* 2021). The transparent wood-epoxy composites also met fire retardancy requirements.

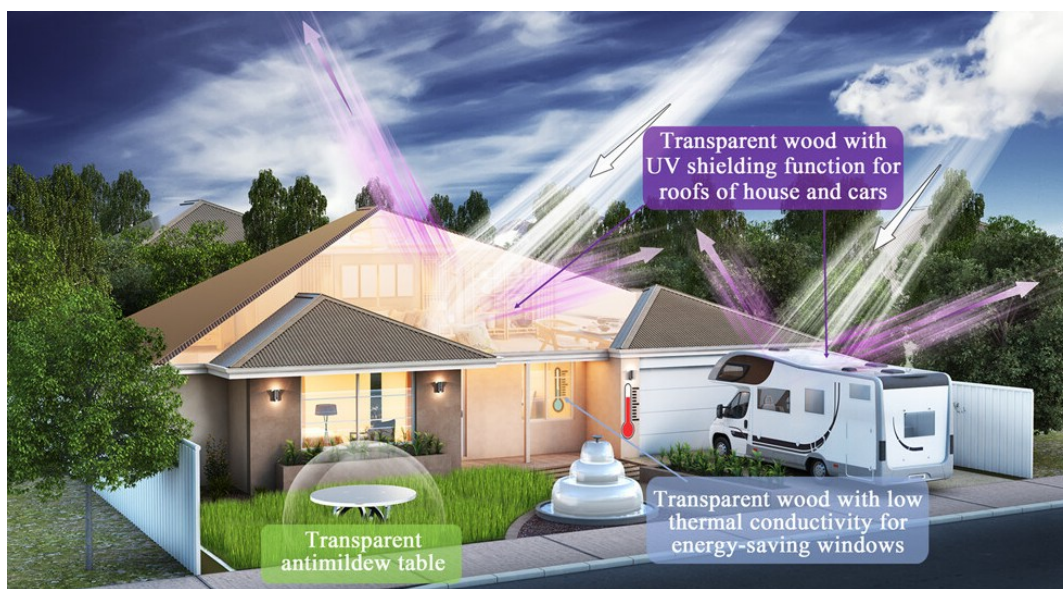

**Fig. 5.** Potential applications of transparent wood composites (de-lignin transparent wood impregnated with PMMA resin and hybrid cerium-doped zinc oxide nanorods as UV-absorbance and reflection fillers) in sustainable buildings (Yang *et al.* 2024). Figure republished with permission from American Chemical Society

The development of intrinsic fire retarding epoxy resins impregnating transparent wood composites sounds promising as an alternatives to glasses (Fan *et al.* 2022). According to our understanding, most transparent wood-based composites are primarily targeting two-dimensional applications currently, *e.g.*, windows and ceilings. By shape transformation and modifications, such technology has the potential to be extended to curved shaped windows and ceilings. Thanks for the shape memory and reworkable properties of epoxy resin vitrimer materials, the epoxy impregnating transparent wood composites have been shown to display excellent editable shape and unique optical performance (Zhang *et al.* 2020; Wang *et al.* 2022). In addition to the optical material applications, the addition of functional particles (*e.g.*, phase change materials) offer the options of transparent wood-vitrimer composites with temperature- and/or color-responsive properties (Qiu *et al.* 2020; Yang *et al.* 2024). This research field is still underdeveloped and there is a need for further research.

### **Sustainable Assessments of Wood-based Structural Composites via Life-Cycle Analysis and Techno-Economic Assessment**

Life cycle (LCA) and techno-economic (TEA) assessments are necessary for sustainability assessment of wood-based structural composite materials. Combining TEA and LCA analysis can comprehensively assess the relationship and trade-offs between economic and environmental impacts of chemically recycled waste polyester derived valuable products-based wood adhesives and commercialized urea-formaldehyde and phenol-formaldehyde adhesives in wood-based structural composite materials. As a quantitatively sustainable analysis method to evaluate the entire process of wood-based structural materials, LCA primarily involves raw material extraction, production of wood-based structural materials, their transportation, use, and waste disposals along with potential environmental impacts. Considering the toxic BPA repeat unit in epoxy and isocyanate repeat unit in polyurethane as wood adhesive, the development of lignin-derived vanillin and eugenol as alternatives to BPA in epoxy and isocyanate-free PU toward environmentally friendly wood adhesives is highly desirable, contributing to truly sustainable wood-based structural composite materials instead of “*pseudo-sustainability*” like the most published works currently. Frankly speaking, this is a tough and long road according to the world research on wood adhesives currently. Thanks for the contribution of “*Simapro*” and “*Open LCA*” software, the awkward situations are becoming alleviated regarding the arguments of “sustainability” in wood adhesives and wood-based structural materials with the evidence of real data supporting.

Regarding TEA challenges of chemically recycled waste polyesters derived valuable products-based wood adhesives in wood-based structural composites, two aspects need to be considered, namely demonstrating technological feasibility and achieving cost competitiveness with conventional adhesives. The cost of obtaining clean recycled plastic feedstock can constitute more than half of the final monomer price. Utilizing cheaper mixed waste plastic streams can mitigate some of these challenges. Although the merits of reworkable epoxy or PU adhesives contribute to the recyclable or remold wood-based structural materials, their additional synthetic protocols need to be minimized or optimized. Such tradeoffs have been shown *via* “*Aspen Plus*” software simulation and calculation to achieve cost-cutting compared to conventional wood adhesives (Yu *et al.* 2025).

## CONCLUSIONS AND FUTURE PROSPECTS

This critical review has focused on the chemical recycling of polyester wastes as a source of value-added chemicals as functional monomers to develop thermoset resins (epoxy and polyurethane, *etc.*) in wood-based advanced structure material applications (*e.g.*, thermoset adhesives and coating). Alcoholysis is emerging gradually as a powerful strategy for chemical upcycling of degradable polyester wastes. However, this process frequently encounters challenges such as low catalytic activity, poor selectivity, and difficulties in product separation. Therefore, the development of suitable catalysts with high efficiency and selectivity is imperative for future research and implementation. Additionally, the direct transesterification reaction is an attractive idea as a new approach transforming the waste PET into valuable polymers (Karanastasis *et al.* 2022; Zhang *et al.* 2023; Fang *et al.* 2024). Such an approach can be extended for vitrimer adhesives and powder coating on wood-based composites (Akkus *et al.* 2019). The direct transesterification upcycling PET approach makes it possible to convert other PBAT waste for advanced wood-based composite applications and antimicrobial and UV block functional transparent wood materials.

The design of new thermoset resin adhesives by utilizing depolymerized monomers or oligomers must incorporate considerations of chemical recyclability for contributing to the sustainability of wood-based structural composite materials. The research on transparent wood composites as the 2.0 Version of wood and plastic composites named WPCs are growing quickly, which is a promising research field for the next decade.

## REFERENCES CITED

- Akkus, M., Akbulut, T., and Candan, Z. (2019). "Application of electrostatic powder coating on wood composite panels using a cooling method. Part 1: Investigation of water intake, abrasion, scratch resistance, and adhesion strength," *BioResources* 14(4), 9557-9574. <https://doi.org/10.15376/biores.14.4.9557-9574>
- Bansode, A., Barde, M., Adjaye, O. A., Patil, V., Hinkle, J., Via, B. K., Adhikari, S., Adamczyk, A. J., Farag, R., Elder, T., Labbé, N., and Auad, M. L. (2021). "Synthesis of biobased novolac phenol-formaldehyde wood adhesives from biorefinery-derived lignocellulosic biomass," *ACS Sustainable Chemistry & Engineering* 9, 10990-11002. <https://doi.org/10.1021/acssuschemeng.1c01916>
- Belyamani, I., Abdelghafar, K., Plouzeau, M., Najemi, L., Askar, K., and Cauret, L. (2025). "Comparative analysis of mechanical recycling simulation of poly(hydroxybutyrate-co-hydroxyvalerate) (PHBV): Injection molding vs. extrusion processes," *Journal of Polymer Science*. Early access. <https://doi.org/10.1002/pol.20250603>
- Cai, H. C., Wang, Z. Q., Xie, D., Zhao, P. P., Sun, J. P., Qin, D. Y., and Cheng, F. C. (2021). "Flexible transparent wood enabled by epoxy resin and ethylene glycol diglycidyl ether," *Journal of Forestry Research* 32, 1779-1787. <https://doi.org/10.1007/s11676-020-01201-y>
- Cevher, D., and Sürdem, S. (2021) "Polyurethane adhesive based on polyol monomers BHET and BHETA depolymerised from PET waste," *International Journal of Adhesion and Adhesives* 105, article 102799. <https://doi.org/10.1016/j.ijadhadh.2020.102799>
- Chatterjee, A., Jha, S., Sen, S., Dev, K., Das, C., and Maji, P. K. (2025). "Hydroxyl-

- functional acrylic adhesives: Leveraging polysilazane chemistry for curing,” *RSC Applied Polymers* 3, 675-685. <https://doi.org/10.1039/D4LP00354C>
- Chen, Y. T., Liu, L. X., Cai, L. J., Mu, G. Q., Ju, T., Wei, M., Li, Z. H., Lu, Z. T., Wang, N., Zhang, T. P., Li, J., Xie, Y. J., and Xiao, S. L. (2024). “High-performance wet adhesion of wood with chitosan,” *ACS Sustainable Chemistry & Engineering* 12, 4946-4956. <https://doi.org/10.1021/acssuschemeng.3c08092>
- Chen, W. W., Wang, Y. W., Zhang, Y., Yuan, D., and Yao, Y. M. (2025). “NaOH-catalyzed alcoholysis of polylactide,” *ACS Sustainable Chemistry & Engineering* 13, 6771-6779. <https://doi.org/10.1021/acssuschemeng.5c02060>
- Chen, X. L., Wang, B., Song, D. P., Pan, L., and Li, Y. S. (2022). “One-step synthesis of sequence-controlled polyester-block-poly(ester-alt-thioester) by chemoselective multicomponent polymerization,” *Macromolecules* 55, 1153-1164. <https://doi.org/10.1021/acs.macromol.1c02303>
- Cheng, K., Hsu, Y., and Uyama, H. (2025). “Solvent-promoted catalyst-free aminolytic degradation for chemical recycling of single and mixed plastic wastes,” *Green Chemistry* 27, article 7620. <https://doi.org/10.1039/D5GC01068C>
- Cheng, M. L., Ying, M. F., Zhao, R. Z., Ji, L. Z., Li, H. X., Liu, X. J., Zhang, J., Li, Y. X., Dong, X. L., and Zhang, X. F. (2022). “Transparent and flexible electromagnetic interference shielding materials by constructing sandwich AgNW@MXene/wood composites,” *ACS Nano* 16, 16996-17007. <https://doi.org/10.1021/acsnano.2c07111>
- Cheung, E., Alberti, C., Bycinskij, S., and Enthaler, S. (2021). “Zinc-catalyzed chemical recycling of poly( $\epsilon$ -caprolactone) applying transesterification reactions,” *Chemistry Select* 6, 8063-8067. <https://doi.org/10.1002/slct.202004294>
- Chuang, C. S., Tsai, K. C., Yang, T. H., Ko, C. H., and Wang, M. K. (2011). “Effects of adding organo-clays for acrylic-based intumescent coating on fire-retardancy of painted thin plywood,” *Applied Clay Science* 53, 709-715. <https://doi.org/10.1016/j.clay.2011.06.009>
- Comí, M., Thys, M., Aerts, A., Geudens, S., Vloemans, S., Feghali, E., Vanbroekhoven, K., and Vendamme, R. (2025). “Revealing the dynamics of sustainable epoxy-acrylate networks from recycled plastics blends and oligomeric lignin precursors,” *ChemSuschem* 18, article 202402375. <https://doi.org/10.1002/cssc.202402375>
- Curley, J. B., Liang, Y. Z., DesVeaux, J. S., Choi, H., Clarke, R. W., Maurya, A. K., Michener, W. E., Stanley, L. M., Wu, Y., Hesse, S. A., Baer, A. L., Neyer, H. A., Tassone, C. J., Jacobsen, A. J., Mante, O. D., Beckham, G. T., and Knauer, K. M. (2025). “Closed-loop recycling of mixed polyesters via catalytic methanolysis and monomer separations,” *Nature Chemical Engineering* 2, 568-580. <https://doi.org/10.1038/s44286-025-00275-x>
- Danielson, M. K., Gainaru, C., Demchuk, Z., Pan, C. Y., Choi, J., Zhang, H. H., Foster, J. C., Saito, T., and Rahman, M. A. (2025). “Closed-loop recyclable vitrimer plastics from PET waste: A design for circularity,” *ChemSusChem*. <https://doi.org/10.1002/cssc.202500898>
- de Carvalho, F. A., Rodrigues, F. R., Dezen, L. E., de Souza, M. V., Santos Junior, A. J., dos Santos, H. F., da Silva, S. A. M., and Christoforo, A. L. (2025). “Eco-friendly particleboard production: Integrating recycled PET and bio-based pine resin adhesives,” *BioResources* 20(2), 3443-3452. <https://doi.org/10.15376/biores.20.2.3443-3452>
- Deacy, A. C., Gregory, G. L., Sulley, G. S., Chen, T. T. D., and Williams, C. K. (2021). “Sequence control from mixtures: Switchable polymerization catalysis and future

- materials applications,” *Journal of the American Chemical Society* 143, 10021-10040. <https://doi.org/10.1021/jacs.1c03250>
- Dedieu, I., Aoufa, C., Gaucela, S., and Peyron, S. (2022). “Mechanical recyclability of biodegradable polymers used for food packaging: case study of polyhydroxybutyrate-co-valerate (PHBV) plastic,” *Food Additives & Contaminants: Part A* 39, 1878-1892. <https://doi.org/10.1080/19440049.2022.2122589>
- Derikvand, M. (2025). “Project-based learning in timber engineering education: A recent example,” *BioResources* 20(1), 17-20. <https://doi.org/10.15376/biores.20.1.17-20>
- Ding, L., Pan, D., Du, K., Li, H., Yu, J. Y., Li, W. Y., Chen, W., Zhang, Y. H., and Tang, Y. (2025). “Zinc-oxide-supported zeolite subcrystal catalyst: Enhancing chemical recycling of poly(lactic acid) via optimized active site dispersion and polymer diffusion,” *ACS Sustainable Chemistry & Engineering* 13, 6665-6674. <https://doi.org/10.1021/acssuschemeng.5c01034>
- Dong, B. Z., Xu, G. Q., Yang, R. L., and Wang, Q. G. (2022). “Upcycling of poly( $\epsilon$ -caprolactone) to valuable chemicals by TBD-catalyzed efficient methanolysis strategy,” *Chemistry an Asian Journal* 17, article 202200667. <https://doi.org/10.1002/asia.202200667>
- Edge, M., Yadav, N., Hmayed, A. A. R., Dove, A. P., and Brandolese, A. (2025). “Continuous flow depolymerization of polycarbonates and poly(lactic acid) promoted by supported organocatalysts,” *ChemSusChem* 18, article 202500420. <https://doi.org/10.1002/cssc.202500420>
- Enayati, M., Mohammadi, S., and Boulido, M. G. (2023). “Sustainable PET waste recycling: labels from PET water bottles used as a catalyst for the chemical recycling of the same bottles,” *ACS Sustainable Chemistry & Engineering* 11, 16618-16626. <https://doi.org/10.1021/acssuschemeng.3c04997>
- Enking, J., Becker, A., Schu, G., Gausmann, M., Cucurachi, S., Tukker, A., and Gries, T. (2025). “Recycling processes of polyester-containing textile waste—A review,” *Resources, Conservation and Recycling* 219, article 108256. <https://doi.org/10.1016/j.resconrec.2025.108256>
- Fan, C. G., Gao, Y. X., Li, Y. H., Yan, L., Zhuang, Y. Z., Zhang, Y., and Wang, Z. Y. (2022). “A flame-retardant and optically transparent wood composite,” *Journal of Applied Polymer Science* 139, article 52945. <https://doi.org/10.1002/app.52945>
- Fan, Z. Q., Li, Y. C., He, J. T., Song, B. Y., Chang, M. Z., Fang, X. Y., Yu, L., Yang, G. C., Guo, H. W., and Liu, Y. (2025). “Bio-based intelligent multifunctional coating for wood: Flame retardancy, fire warning, smoke suppression, thermal insulation and antibacterial activity,” *Construction and Building Materials* 465, article 140244. <https://doi.org/10.1016/j.conbuildmat.2025.140244>
- Fang, T. X., Jiang, W. P., Zheng, T. F., Yao, X. X., and Zhu, W. P. (2024). “Catalyst- and solvent-free upcycling of poly(ethylene terephthalate) waste to biodegradable plastics,” *Advanced Materials* 36, article 2403728. <https://doi.org/10.1002/adma.202403728>
- Feghali, E., Tauk, L., Ortiz, P., Vanbroekhoven, K., and Eevers, W. (2020). “Catalytic chemical recycling of biodegradable polyesters,” *Polymer Degradation and Stability* 179, article 109241. <https://doi.org/10.1016/j.polymdegradstab.2020.109241>
- Figalla, S., Jašek, V., Fučík, J., Menčík, P., and Příkryl, R. (2024). “Poly(lactide) upcycling approach through transesterification for stereolithography 3D printing,” *Biomacromolecules* 25, 6645-6655. <https://doi.org/10.1021/acs.biomac.4c00840>
- Gabirondo, E., Maiz-Iginitz, A., Ximenis, M., Świderek, K., Sanz, D. A., Moliner, V.,

- Cabedo, L., Westlie, A. H., Chen, Cerrón-Infantes, D. A., Unterlass, M. M., López-Gallego, F., Etxeberria, A., and Sardon, H. (2025). “Selective chemical recycling of polyhydroxybutyrate into high-value hydroxy acid using taurine organocatalyst,” *Chemical Science*. <https://doi.org/10.1039/D5SC02196K>
- Gao, X., Wang, Z., Zhang, M. H., Yu, Y. K., Zhang, S. Y., and Mei, Q. Q. (2025). “From solvent to catalyst: In situ amino acid-like species enable PET upcycling without added catalysts,” *Angewandte Chemie International Edition* 64, article 202513723. <https://doi.org/10.1002/anie.202513723>
- Garcia, R., Calvez, I., Koubaa, A., Landry, V., and Cloutier, A. (2024). “Sustainability, circularity, and innovation in wood-based panel manufacturing in the 2020s: Opportunities and challenges,” *Current Forestry Report* 10, 420-441. <https://doi.org/10.1007/s40725-024-00229-1>
- Gašparík, M., Makovická Osvaldová, L., Čekovská, H., and Potůček, D. (2017). “Flammability characteristics of thermally modified oak wood treated with a fire retardant,” *BioResources* 12(4), 8451-8467. <https://doi.org/10.15376/biores.12.4.8451-8467>
- Ghahri, S., Yang, L., Du, G., and Park, B.-D. (2025). “Transition from formaldehyde-based wood adhesives to bio-based alternatives,” *BioResources* 20(2), 2476-2479. <https://doi.org/10.15376/biores.20.2.2476-2479>
- Godinho, B., Gama, N., Barros-Timmons, A., and Ferreira, A. (2021). “Recycling of polyurethane wastes using different carboxylic acids via acidolysis to produce wood adhesives,” *Journal of Polymer Science* 59, 697-705. <https://doi.org/10.1002/pol.20210066>
- Gonçalves, D., Bordado, J. M., Marques, A. C., and dos Santos, R. G. (2021). “Non-formaldehyde, bio-based adhesives for use in wood-based panel manufacturing industry—A review,” *Polymers* 13, article 4086. <https://doi.org/10.3390/polym13234086>
- Gupta, V., and Sarkar, R. (2025). “Closed-loop recycling of covalent adaptable network (CAN) derived from dopamine and waste PET,” *Journal of Polymer Science* 63, 2237-2247. <https://doi.org/10.1002/pol.20250313>
- Hao, W. T., Zheng, Q. N., Zhong, Y. N. J., Meng, X. K., Wang, H. L., Qiu, L. Z., Lu, H. B., Huang, Y. P., and Yang, W. (2023). “An eco-friendly and facile method to prepare waterborne polyurethane based fire-resistant & waterproof coatings for wood protection,” *Progress in Organic Coatings* 185, article 107892. <https://doi.org/10.1016/j.porgcoat.2023.107892>
- Hiemenz, P. C., and Lodge, T. P. (2007). *Polymer Chemistry*, 2<sup>nd</sup> Ed., Boca Raton, United States.
- Hoadley, R. B. (2000). *Understanding Wood, A Craftsman's Guide to Wood Technology*.
- Hoang C. N., Nguyen, N. T., Ta, S. T., Nguyen, N. N., and Hoang, D. Q. (2022). “Acidolysis of poly(ethyleneterephthalate) waste using succinic acid under microwave irradiation as a new chemical upcycling method,” *ACS Omega* 7, 47285-47295. <https://doi.org/10.1021/acsomega.2c06642>
- Hofmann, M., Alberti C., Scheliga, F., Meißner, R. R. R., and Enthaler, S. (2020). “Tin(II) 2-ethylhexanoate catalysed methanolysis of end-of-life poly(lactide),” *Polymer Chemistry* 11, 2625-2629. <https://doi.org/10.1039/D0PY00292E>
- Hosseinashrafi, S. K., Hosseinihashemi, S. K., Gorji, P., and Akhtari, M. (2023). “Environment-friendly waterborne fire retardants for protection of wood and bark against fire flames,” *BioResources* 18(4), 7681-7699.

- <https://doi.org/10.15376/biores18.4.7681-7699>
- Hubble, D., Nordahl, S., Zhu, T. Y., Baral, N., Scown, C. D., and Liu, G. (2023). “Solvent-assisted poly(lactic acid) upcycling under mild conditions,” *ACS Sustainable Chemistry & Engineering* 11, 8208-8216. <https://doi.org/10.1021/acssuschemeng.2c06500>
- Huzyan, H. I., Abdul Aziz, A., and Hussin, M. H. (2021). “Ecofriendly wood adhesives from date palm fronds lignin for plywood,” *BioResources* 16(2), 4106-4125. <https://doi.org/10.15376/biores.16.2.4106-4125>
- Jang, E.-S., Jo, S.-U., and Park, H.-J. (2025). “Fire safety performance of radiata pine-magnesium-laminated (RML) board for building material,” *BioResources* 20(3), 5620-5632. <https://doi.org/10.15376/biores.20.3.5620-5632>
- Jašek, V., Fučík, J., Ivanová, L., Veselý, D., Figalla, S., Mravcova, L., Sedlacek, P., Krajčovič, J., and Příkry, R. (2022). “High-pressure depolymerization of poly(lactic acid) (PLA) and poly(3-hydroxybutyrate) (PHB) using bio-based solvents: A way to produce alkyl esters which can be modified to polymerizable monomers,” *Polymers* 14, article 5236. <https://doi.org/10.3390/polym14235236>
- Jia, C., Chen, C. J., Mi, R. Y., Li, T., Dai, J. Q., Yang, Z., Pei, Y., He, S. M., Bian, H. Y., Jang, S. H., Zhu, J. Y., Yang, B., and Hu, L. B. (2019). “Clear wood toward high-performance building materials,” *ACS Nano* 13, 9993-10001. <https://doi.org/10.1021/acsnano.9b00089>
- Jia, Z. X., Gao, L., Qin, L. J., and Yin, J. Z. (2023). “Chemical recycling of PET to value-added products,” *RSC Sustainability* 1, 2135-2147. <https://doi.org/10.1039/D3SU00311F>
- Jin, X. B., Jiang, Z. H., Wen, X. W., Zhang, R., and Qin, D. C. (2017). “Flame retardant properties of laminated bamboo lumber treated with monoammonium phosphate (MAP) and boric acid/borax (SBX) compounds,” *BioResources* 12(3), 5071-5085. DOI: 10.15376/biores.12.3.5071-5085
- Karanastasis, A. A., Safin, V., and Pitet, L. M. (2022). “Bio-based upcycling of poly(ethylene terephthalate) waste for the preparation of high-performance thermoplastic copolyesters,” *Macromolecules* 55, 1042-1049. <https://doi.org/10.1021/acs.macromol.1c02338>
- Lahive, C. W., Dempsey, S. H., Reiber, S. E., Pal, A., Stevenson, K. R., Michener, W. E., Alt, H. M., Ramirez, K. J., Rognerud, E. G., Lincoln, C. L., Clarke, R. W., DesVeaux, J. S., Uekert, T., Rorrer, N. A., Knauer, K. M., and Beckham, G. T. (2025). “Acetolysis for epoxy-amine carbon fibre-reinforced polymer recycling,” *Nature* 642, 605-612. <https://doi.org/10.1038/s41586-025-09067-y>
- Leibfarth, F. A., Moreno, N., Hawker, A. P., and Shand, J. D. (2012). “Transforming polylactide into value-added materials,” *Journal of Polymer Science Part A: Polymer Chemistry* 50, 4814-4822. <https://doi.org/10.1002/pola.26303>
- Lehnertz, M. S., Mensah, J. B., and Palkovits, R. (2022). “Chemical recycling of polyhydroxybutyrate and polylactic acid over supported Ru catalysts,” *Green Chemistry* 24, 3957-3963. <https://doi.org/10.1039/D2GC00216G>
- Li, C. J., Wang, L. Y., Yan, Q., Liu, F. S., Shen, Y., and Li, Z. B. (2022). “Rapid and controlled polymerization of bio-sourced  $\delta$ -caprolactone toward fully recyclable polyesters and thermoplastic elastomers,” *Angewandte Chemie International Edition* 134, Article 202204407. <https://doi.org/10.1002/ange.202201407>
- Li, M. L., Hao, X. H., Hu, M. L., Huang, Y. H., Qiu, Y., Li, and L. P. (2022). “Synthesis of bio-based flame-retardant epoxy co-curing agent and application in wood surface

- coating,” *Progress in Organic Coatings* 167, article 106848.  
<https://doi.org/10.1016/j.porgcoat.2022.106848>
- Li, N., Li, Z. X., Cui, Y. L., Liang, L., Peng, W. C., Cheng, Z. J., Yan, B. B., and Chen, G. Y. (2025). “Chemical upcycling of biodegradable plastic waste: A critical review,” *Green Chemistry* 27, 9000-9015. <https://doi.org/10.1039/D5GC02078F>
- Li, R., Li, L. F., Qiu, W. L., Zhu, D. Y., Qiu, X. Q., Ou, R. X., Liu, B. H., and Liu, W. F. (2025). “Sustainable waterborne polyurethane adhesive with superstrong adhesion performance and excellent weatherability from biomass lignin and CO<sub>2</sub>-based polyols,” *Advanced Functional Materials* 2024, article 2422605.  
<https://doi.org/10.1002/adfm.202422605>
- Li, R. X., Zeng, W., Zhao, Y. F., Li, G. X., Fu, J. F., Zhang, F. T., Wang, Y. S., Zhang, H., Tang, M. H., Liu, D. L., Zhao, R. Y., Han, B. X., and Liu, Z. M. (2025). “Complete recycling of polyester wastes with dialkyl carbonates,” *Angewandte Chemie International Edition*. <https://doi.org/10.1002/anie.202518885>
- Li, Z., Shen, Y., and Li, Z. B. (2024). “Ring-opening polymerization of lactones to prepare closed-loop recyclable polyesters,” *Macromolecules* 57, 1919-1940.  
<https://doi.org/10.1021/acs.macromol.3c01912>
- Lian, X. B., Li, Y. B., Li, P. H., Jin, Y. L., Zhao, X. Y., Li, J. W., Kong, D. H., Zhao, S. J., Xiang, S. F., Fu, F. Y., and Liu, X. D. (2025). “Wood-inspired dynamic covalent cross-linking network for ultrahigh adhesion strength, desired weather resistance, and closed-loop recycling adhesives,” *ACS Applied Materials and Interfaces* 17, 47707-47718. <https://doi.org/10.1021/acscami.5c10343>
- Liang, Y. Q., Zuo, H. W., Wen, M. Y., Shi, J. Y., and Park, H. (2025). “Self-healing, flame retardant and UV resistant lignin-derived epoxy wood coating with a Schiff base structure,” *International Journal of Biological Macromolecules* 286, article 138393. <https://doi.org/10.1016/j.ijbiomac.2024.138393>
- Lin, B. H., and Waymouth, R. M. (2018). “Organic ring-opening polymerization catalysts: Reactivity control by balancing acidity,” *Macromolecules* 51, 2932-2938.  
<https://doi.org/10.1021/acs.macromol.8b00540>
- Liu, J. J., Liu, Y., Hou, Z. Y., Ju, T., Lou, Y. H., Tong, Z. H., Liu, S., Sun, J. S., Xia, Q. Q., and Yu, H. P. (2024). “One-step synthesis of waterborne epoxidized lignin nanoparticles with high epoxy value and stability for high-strength adhesives,” *ACS Sustainable Chemistry & Engineering* 12, 15376-15386.  
<https://doi.org/10.1021/acssuschemeng.4c02695>
- Liu, J., Pich, A., and Bernaerts, K. V. (2024). “Preparation of lignin-based vinylogous urethane vitrimer materials and their potential use as on-demand removable adhesives,” *Green Chemistry* 26, article 1414. <https://doi.org/10.1039/D3GC02799F>
- Liu, K. Y., and Li, C. W. (2025). “Lignin bleaching based N-P-Si ternary synergistic system for the construction of transparent wood: integration of fire protection and hydrophobic properties,” *International Journal of Biological Macromolecules* 320, article 146013. <https://doi.org/10.1016/j.ijbiomac.2025.146013>
- Liu, M. S., Guo, J., Gu, Y. Q., Gao, J., and Liu, F. S. (2018). “Versatile imidazole-anion-derived ionic liquids with unparalleled activity for alcoholysis of polyester wastes under mild and green conditions,” *ACS Sustainable Chemistry & Engineering* 6, 15127-15134. <https://doi.org/10.1021/acssuschemeng.8b03591>
- Liu, Q. Y., Yang, Y. L., Dong, B. Z., Sun, H. G., Xu, G. Q., and Wang, Q. G. (2024). “Ultrafast and selective chemical recycling of PLA to methyl lactate by using MHMDS as simple catalysts,” *Polymer Degradation and Stability* 222, article

110706. <https://doi.org/10.1016/j.polymdegradstab.2024.110706>
- Liu, S., Hu, L., Liu, J. Y., Zhang, Z. S., Suo, H. Y., and Qin, Y. S. (2024). “Zinc catalyst for chemical upcycling of PLA wastes: Novel industrial monomer resource toward poly(ester–amide),” *Macromolecules* 57, 4662-4669. <https://doi.org/10.1021/acs.macromol.4c00360>
- Luo, H., Tyrrell, H., Bai, J. Y., Muazu, R. I., and Long, X. Y. (2024). “Fundamental, technical and environmental overviews of plastic chemical recycling,” *Green Chemistry* 26, article 11444. <https://doi.org/10.1039/D4GC03127J>
- Luo, Z. X., Tian, G. Q., Chen, S. C., Wu, G., and Wang, Y. Z. (2024). “Solvent-free one-pot recycling of polylactide to usable polymers and their closed-loop recyclability,” *Macromolecules* 57, 6828-6837. <https://doi.org/10.1021/acs.macromol.4c01104>
- Majgaonkar, P., Hanich, R., Malz, F., and Brüll, R. (2021). “Chemical recycling of post-consumer PLA waste for sustainable production of ethyl lactate,” *Chemical Engineering Journal* 423, article 129952. <https://doi.org/10.1016/j.cej.2021.129952>
- Marullo, S., Dintcheva, C. R. N. T., and D’Anna, F. (2021). “Amino acid based cholinium ionic liquids as sustainable catalysts for PET depolymerization,” *ACS Sustainable Chemistry & Engineering* 9, 15157-15165. <https://doi.org/10.1021/acssuschemeng.1c04060>
- McKeown, P., and Jones, M. D. (2020). “The chemical recycling of PLA: A review,” *Sustainable Chemistry* 1, 1-22. <https://doi.org/10.3390/suschem1010001>
- Millucci, F., Germani, R., Colelli, L., Gabrielli, S., Sassi, P., Donnadio, A., Conti, M., and Corez, S. (2025). “Overcoming hydrophobicity with water enables ultrafast hydrolysis of waste polyethylene terephthalate at very mild conditions,” *Angewandte Chemie International Edition* article 14136. <https://doi.org/10.1002/anie.202514136>
- Mittal, N., Soni, R. K., and Teotia, M. (2025). “Innovative approaches to chemical recycling of polyethylene terephthalate waste: Investigating key components and their emerging applications,” *Journal of Environmental Management* 373, article 123595. <https://doi.org/10.1016/j.jenvman.2024.123595>
- Mohammadi, S., Bouldo, M. G., and Enayati, M. (2023). “Controlled glycolysis of poly(ethylene terephthalate) to oligomers under microwave irradiation using antimony (III) oxide,” *ACS Applied Polymer Materials* 5, 6574-6584. <https://doi.org/10.1021/acsapm.3c01071>
- Mousavi, S. Y., Huang, J., and Li, K. C. (2019). “Investigation of epoxy-based wood adhesives,” *Journal of Applied Polymer Science* 136, article 47741. <https://doi.org/10.1002/app.47741>
- Muangmeesri, S., Baddigam, K. R., Navare, K., Apostolopoulou-Kalkavoura, V., Witthayolankowit, K., Håkansson, H., Mathew, A. P., Acker, K. V., and Samec, J. S. M. (2024) “Recycling of polyesters by organocatalyzed methanolysis depolymerization: Environmental sustainability evaluated by life cycle assessment,” *ACS Sustainable Chemistry & Engineering* 12, 4114-4120. <https://doi.org/10.1021/acssuschemeng.3c07435>
- Neitzel, N., Hosseinpourpia, R., and Adamopoulos, S. (2023). “A dialdehyde starch-based adhesive for medium-density fiberboards,” *BioResources* 18(1), 2155-2171. <https://doi.org/10.15376/biores.18.1.2155-2171>
- Nim, B., Opaprakasit, M., Petchsuk, A., and Opaprakasit, P (2020). “Microwave-assisted chemical recycling of polylactide (PLA) by alcoholysis with various diols,” *Polymer Degradation and Stability* 181, article 109363. <https://doi.org/10.1016/j.polymdegradstab.2020.109363>

- Nim, B., Rahayu, S. S., Thananukul, K., Eang, C., Opaprakasit, M., Petchsuk, A., Kaewsaneha, C., Polpanich, D., and Opaprakasit, P. (2023). "Sizing down and functionalizing polylactide (PLA) resin for synthesis of PLA-based polyurethanes for use in biomedical applications," *Scientific Reports* 13, article 2284. <https://doi.org/10.1038/s41598-023-29496-x>
- Odian, G. (2007). *Principles of Polymerization* (4<sup>th</sup> Ed.), Wiley, Hoboken, NJ, USA.
- Olazabal, I., Barrios, E. J. L., Meester, S. D., Jehanno, C., and Sardon, H. (2024). "Overcoming the limitations of organocatalyzed glycolysis of poly(ethylene terephthalate) to facilitate the recycling of complex waste under mild conditions," *About ACS Applied Polymer Materials* 6, 4226-4232. <https://doi.org/10.1021/acsapm.4c00326>
- Parodi, A., Arpaia, A., Samorì, C., Mazzocchetti, L., and Galletti, P. (2023). "Novel strategies for recycling poly(butyleneadipate-co-terephthalate)-starch-based plastics: Selective solubilization and depolymerization–repolymerization processes," *ACS Sustainable Chemistry & Engineering* 11, 14518-14527. <https://doi.org/10.1021/acssuschemeng.3c03588>
- Peng, J. D., Liu, F. F., Feng, F. Q., Feng, X. P., and Cui, J. Q. (2023). "Enhancing environmentally friendly tannin adhesive for plywood through hyperbranched polyamide," *ACS Sustainable Chemistry & Engineering* 11, 13805-13811. <https://doi.org/10.1021/acssuschemeng.3c04301>
- Petrus, R., Bykowski, D., and Sobota, P. (2016). "Solvothermal alcoholysis routes for recycling polylactide waste as lactic acid esters," *ACS Catalysis* 6, 5222-5235. <https://doi.org/10.1021/acscatal.6b01009>
- Phetphaisit, C. W., Bumee, R., Namahoot, J., Ruamcharoen, J., and Ruamcharoen, P. (2013). "Polyurethane polyester elastomer: Innovative environmentally friendly wood adhesive from modified PETs and hydroxyl liquid natural rubber polyols," *International Journal of Adhesion & Adhesives* 41, 127-131. <https://doi.org/10.1016/j.ijadhadh.2012.11.007>
- Popović, J., Svrzić, S., Gajić, M., Maletić, S., Dodevski, V., Djiporović-Momčilović, M., Krstić, S., and Popović, M. (2022). "Light transmittance of mahogany wood treated with 20% hydrogen peroxide solution," *BioResources* 17(4), 5919-5935. <https://doi.org/10.15376/biores.17.4.5919-5935>
- Pu, M. Y., Fang, C. Q., Zhou, X., Bai, T. Q., Lin, Y. Y., and Lei, W. Q. (2024). "Sustainable and renewable microcross-linked polyurethane pressure-sensitive adhesive from waste polyethylene terephthalate," *ACS Sustainable Chemistry & Engineering* 12, 12226-12235. <https://doi.org/10.1021/acssuschemeng.4c04411>
- Qin, L. D., Li, X. X., Ren, G., Yuan, R. Y., Wang, X. Y., Hu, Z. X., Ye, C. X., Zou, Y. Y., Ding, P. Q., Zhang, H. J., and Cai, Q. Q. (2024). "Closed-loop polymer-to-polymer upcycling of waste poly (ethylene terephthalate) into biodegradable and programmable materials," *ChemSusChem* 17, article 202301781. <https://doi.org/10.1002/cssc.202301781>
- Qiu, Z., Wang, S., Wang, Y. G., Li, J., Xiao, Z. F., Wang, H. G., Liang, D. X., and Xie, Y. J. (2020). "Transparent wood with thermo-reversible optical properties based on phase-change material," *Composites Science and Technology* 20, article 108407. <https://doi.org/10.1016/j.compscitech.2020.108407>
- Román-Ramírez, L. A., McKeown, P., Shah, C., Abraham, J., Jones, M. D., and Wood, J. (2020). "Chemical degradation of end-of-life poly(lactic acid) into methyl lactate by a Zn(II) complex," *Industrial & Engineering Chemistry Research* 59, 11149-11156.

- <https://doi.org/10.1021/acs.iecr.0c01122>
- Saito, K., Eisenreich, F., Türel, T., and Tomović, Z. (2022). “Closed-loop recycling of poly(imine-carbonate) derived from plastic waste and bio-based resources,” *Angewandte Chemie International Edition* 61, article 202211806. <https://doi.org/10.1002/ange.202211806>
- Saito, K., Schara, P., Eisenreich, F., and Tomović, Ž. (2025). “One-step conversion of bisphenol A polycarbonate into aliphatic polycarbonate polyols for recyclable polyurethane production,” *Chemistry-A European Journal*, article 202501819. <https://doi.org/10.1002/chem.202501819>
- Saito, T., Aizawa, Y., Yamamoto, T., Tajima, K., Isono, T., and Satoh, T. (2018). “Alkali metal carboxylate as an efficient and simple catalyst for ring-opening polymerization of cyclic esters,” *Macromolecules* 51, 689-696. <https://doi.org/10.1021/acs.macromol.7b02566>
- Senra, E. M., Silva, A. L. N., and Pacheco, E. B. A. V. (2023). “A review of waterborne polyurethane coatings and adhesives with polyester polyol from poly(ethylene terephthalate) waste,” *Journal of Polymers and the Environment* 31, 3719-3739. <https://doi.org/10.1007/s10924-023-02836-8>
- Shmulsky, R., Jones, P. D., and Lilley, K. (2011). *Forest Products and Wood Science, An Introduction* (6<sup>th</sup> Ed.), Wiley, Hoboken, NJ, USA
- Shi, C. X., Quinn, E. C., Diment, W. T., and Chen, E. Y. X. (2024). “Recyclable and (bio)degradable polyesters in a circular plastics economy,” *Chemical Reviews* 124, 4393-4478. <https://doi.org/10.1021/acs.chemrev.3c00848>
- Solomons, T. W. G., and Fryhle, C. B. (2011). *Organic Chemistry* (10<sup>th</sup> Ed.), Wiley, Hoboken, NJ, USA.
- Sombatsompop, N., Srimalanon, P., Markpin, T., and Prapagdee, B. (2021). “Polylactic acid (PLA): Improve it, use it, and dump it faster,” *BioResources* 16(2), 2196-2199. <https://doi.org/10.15376/biores.16.2.2196-2199>
- Song, S. Y., Liu, F. S., Wang, H., Wang, C., Yu, S. T., and Liu, S. W. (2018). “Methanolysis of microbial polyester poly(3-hydroxybutyrate) catalyzed by Brønsted-Lewis acidic ionic liquids as a new method towards sustainable development,” *Polymer Degradation and Stability* 147, 215-221. <https://doi.org/10.1016/j.polymdegradstab.2017.12.009>
- Song, X. Y., Wang, H., Liu, F. X., and Yu, S. T. (2016). “Kinetics and mechanism of monomeric product from methanolysis of poly (3-hydroxybutyrate) catalyzed by acidic functionalized ionic liquids,” *Polymer Degradation and Stability* 130, 22-29. <https://doi.org/10.1016/j.polymdegradstab.2016.05.023>
- Song, X. Y., Wang, H., Wang, C., Liu, F. S., Yu, S. T., Liu, S. W., and Song, Z. Y. (2019). “Chemical recycling of bio-based poly(3-hydroxybutyrate) wastes under methanolysis condition catalyzed by Fe-containing magnetic ionic liquid,” *Journal of Polymers and the Environment* 27, 862-870. <https://doi.org/10.1007/s10924-018-1347-8>
- Song, X. Y., Wang, C., Shen, Y., Liu, F. S., Yu, S. T., and Ge, X. P. (2018). “Methanolysis of poly(3-hydroxybutyrate) catalyzed by ferric chloride,” *Advances in Polymer Technology* 37, 2915-2921. <https://doi.org/10.1002/adv.21963>
- Spicer, A. J., Brandolese, A., and Dove, A. P. (2024). “Selective and sequential catalytic chemical depolymerization and upcycling of mixed plastics,” *ACS Macro Letters* 13, 189-194. <https://doi.org/10.1021/acsmacrolett.3c00751>
- Sun, Y., Qiu, X., and Lan, X. (2025). “Modified lignin–PVOH and epoxy adhesives for

- engineered wood," *BioResources* 20(3), 6406-6425.  
<https://doi.org/10.15376/biores.20.3.6406-6425>
- Tan, B. B., Lv, M., Qi, X. T., and Huang, Z. L. (2025). "Hydrogenation-induced selective degradation of PET wastes," *Green Chemistry*. <https://doi.org/10.1039/D5GC02071A>
- Tan, Y., Wang, K. L., Dong, Y. M., Gong, S. S., Lu, Y., Shi, S. Q., and Li, J. Z. (2024). "Programmable and shape-color synchronous dual-response wood with thermal stimulus," *ACS Nano* 18, 6718-6730. <https://doi.org/10.1021/acsnano.3c03607>
- Tang, Q. H., Zou, M., Gao, K. Z., Chang, L., Gao, L., and Guo, W. J. (2021). "Laminating delignified wood veneers toward high-strength, flame-retardant composites for structural applications," *ACS Sustainable Chemistry & Engineering* 9, 10717-10726. <https://doi.org/10.1021/acssuschemeng.0c09390>
- Thoma, J. L., Elsener, R., Burgert, I., and Schubert, M. (2024). "Chemical and physical debonding-on-demand of poly(urethane urea) thermoset adhesives to facilitate the recycling of engineered wooden products," *ACS Applied Polymer Materials* 6, 5778-5787. <https://doi.org/10.1021/acsapm.4c00439>
- Tu, W., Chu, H., Huang, C., Chen, C., Ou, C., and Guo, G. (2022). "Polyhydroxy-alkanoate production by *Cupriavidus necator* with inedible rice," *BioResources* 17(2), 2202-2213. <https://doi.org/10.15376/biores.17.2.2202-2213>
- Wang, H., Liang, J., Zhang, J., Zhou, X., and Du, G. (2017). "Performance of urea-formaldehyde adhesive with oxidized cassava starch," *BioResources* 12(4), 7590-7600. <https://doi.org/10.15376/biores.12.4.7590-7600>
- Wang, K. L., Liu, X. R., Dong, Y. M., Ling, Z., Cai, Y. H., Tian, D., Fang, Z., and Li, J. Z. (2022). "Editable shape-memory transparent wood based on epoxy-based dynamic covalent polymer with excellent optical and thermal management for smart building materials," *Cellulose* 29, 7955-7972. <https://doi.org/10.1007/s10570-022-04754-9>
- Wang, N., Zhang, Q., Sun, Z. Q., Zhang, H., Hu, C. Y., Sun, H., Pang, X., and Chen, X. S. (2025). "Recycling polyester and polycarbonate plastics with carbocation Lewis acidic organocatalysts," *ACS Macro Letters* 14, 377-384.  
<https://doi.org/10.1021/acsmacrolett.5c00054>
- Wang, Y. Z., Yang, R. L., Xu, G. Q., Guo, X. H., Dong, B. Z., Zhang, Q. F., Li, R., and Wang, Q. G. (2023). "Zn-catalyzed coordination-insertion depolymerization strategy of poly(3-hydroxybutyrate) under bulk conditions," *Polymer Degradation and Stability* 214, article 110413. <https://doi.org/10.1016/j.polymdegradstab.2023.110413>
- Wang, Z., Kang, H. J., Liu, H. G., Zhang, S. F., Xia, C. L., Wang, Z. K., and Li, J. Z. (2020). "Dual-network nanocross-linking strategy to improve bulk mechanical and water-resistant adhesion properties of biobased wood adhesives," *ACS Sustainable Chemistry & Engineering* 8, 16430-16440.  
<https://doi.org/10.1021/acssuschemeng.0c04913>
- Wei, K., Ng, J., Lim, J. S. K., Gupta, N., Dong, B. X., Hu, C. P., Hu, J. D., and Hu, X. W. (2023). "A facile alternative strategy of upcycling mixed plastic waste into vitrimers," *Communications Chemistry* 6, article 158. <https://doi.org/10.1038/s42004-023-00949-8>
- Wu, J., Wang, M., and Guo, H. (2017). "Synergistic flame retardant effects of different zeolites on intumescent fire retardant coating for wood," *BioResources* 12(3), 5369-5382. <https://doi.org/10.15376/biores.12.3.5369-5382>
- Wu, J. Y., Yang, F., Shi, D. D., Miao, Z., Wang, J., Wang, D. Y., and Zhang, Y. D. (2025). "Converting waste polyethylene terephthalate to high value monomers by synergistic catalysts," *ChemSusChem* 18, article 202401922.

- <https://doi.org/10.1002/cssc.202401922>
- Wu, W. H., Zhai, H. J., Wu, K. T., Wang, X., Rao, W. H., Ding, J. D., and Yu, L. (2024). “Cheap organocatalyst diphenyl phosphate for efficient chemical recycling of poly(lactic acid), other polyesters and polycarbonates,” *Chemical Engineering Journal* 480, article 148131. <https://doi.org/10.1016/j.cej.2023.148131>
- Xie, S. Q., Wang, C. Q., Hu, W. D., Hu, J. Z., Wang, Y., Dong, Z., Intan, N. N., Pfaendtner, J., and Lin, H. F. (2024). “Chemical recycling of post-consumer polyester wastes using a tertiary amine organocatalyst,” *Cell Reports Physical Science* 5, article 102145. <https://doi.org/10.1016/j.xcrp.2024.102145>
- Xin, Y. Z., Che, C. X., Yuan, F., Jia, R. R., Chen, P., Shi, L. Y., and Huang, L. (2025). “Closed-loop recycling of depolymerizing poly(butylene succinate) as chemical monomers,” *Industrial & Engineering Chemistry Research* 64, 4627-4636. <https://doi.org/10.1021/acs.iecr.4c04533>
- Xu, Z., Sanchez-Rivera, K., Granger, C., Zhou, P. Z., del Carmen Munguia-Lopez, A., Ikegwu, U. W., Avraamidou, S., Zavala, V. M., Van Lehn, R. C., Bar-Ziv, E., Meester, S. D., and Huber, G. W. (2025). “Solvent-based plastic recycling technologies,” *Nature Chemical Engineering* 2, 407-423. <https://doi.org/10.1038/s44286-025-00247-1>
- Yang, R. L., Xu, G. Q., Dong, B. Z., Hou, H. B., and Wang, Q. G. (2022). “A ‘polymer to polymer’ chemical recycling of PLA plastics by the ‘DE-RE polymerization’ strategy,” *Macromolecules* 55, 1726-1735. <https://doi.org/10.1021/acs.macromol.1c02085>
- Yang, Y. D., Liu, X. Y., Wan, C. C., Liu, S. L., Li, X. G., Zhu, Y., Yang, Z. X., Li, L. L., Zhang, Z., Zhou, Z. Y., Xie, Y. Z., Zhao, X. P., Chai, H. Y., and Wu, Y. Q. (2024). “Powering the future green buildings: Multifunctional ultraviolet-shielding transparent wood,” *ACS Nano* 18, 21288-21301. <https://doi.org/10.1021/acsnano.4c05151>
- Yang, Y. L., Xu, G. Q., Dong, B. Z., Guo, X. H., and Wang, Q. G. (2022). “Selective, sequential, and “one-pot” depolymerization strategies for chemical recycling of commercial plastics and mixed plastics,” *ACS Sustainable Chemistry & Engineering* 10, 9860-9871. <https://doi.org/10.1021/acssuschemeng.2c01708>
- Yang, X. L., Tian, Z. W., Duan, G. G., Zhang, C. M., Han, X. S., Yang, H. Q., Han, J. Q., He, S. J., and Jiang, S. H. (2024). “Light-responsive multimode luminescence in photochromism transparent wood for anti-counterfeiting application,” *Industrial Crops and Products* 219, Article 119098. <https://doi.org/10.1016/j.indcrop.2024.119098>
- Yu, Y. K., Zhang, Y. F., Zhu, S. M., and Mei, Q. Q. (2025). “Cost-effective and low-carbon scalable recycling of waste polyethylene terephthalate through bio-based guaiacol-enhanced methanolysis,” *Angewandte Chemie International Edition* 64, article 202503469. <https://doi.org/10.1002/anie.202503469>
- Yuan, J. S., Xiong, W., Zhou, X. H., Zhang, Y., Shi, D., Li, Z. C., and Lu, H. (2019). “4-hydroxyproline-derived sustainable polythioesters: Controlled ring-opening polymerization, complete recyclability, and facile functionalization,” *Journal of the American Chemical Society* 141, 4928-4935. <https://doi.org/10.1021/jacs.9b00031>
- Yue, D., Fu, G., and Jin, Z. (2021). “Transparent wood prepared by polymer impregnation of rubber wood (*Hevea brasiliensis* Muell. Arg),” *BioResources* 16(2), 2491-2502. <https://doi.org/10.15376/biores.16.2.2491-2502>
- Zhang, H. J., Fang, T. X., Yao, X. X., Li, X. D., and Zhu, W. P. (2023). “Catalytic

- amounts of an antibacterial monomer enable the upcycling of poly(ethylene terephthalate) waste,” *Advanced Materials* 35, article 2210758. <https://doi.org/10.1002/adma.202210758>
- Zhang, L. M., Wang, A., Zhu, T. L., Chen, Z., Wu, Y. P., and Gao, Y. F. (2020). “Transparent wood composites fabricated by impregnation of epoxy resin and W-doped VO<sub>2</sub> nanoparticles for application in energy-saving windows,” *ACS Applied Materials & Interfaces* 12, 34777-34783. <https://doi.org/10.1021/acsami.0c06494>
- Zhang, Q., Hu, C. Y., Li, P. Y., Bai, F. Q., Pang, X., and Chen, X. S. (2024). “Solvent-promoted catalyst-free recycling of waste polyester and polycarbonate materials,” *ACS Macro Letters* 13, 151-157. <https://doi.org/10.1021/acsmacrolett.3c00581>
- Zhang, Y. L., Ou, S. Y., Peng, Z. H., Qi, Y. Z., Chen, C. T., Zhuo, G. W., Liao, J. Q., Li, L. P., Liu, M. L., and Guo, C. G. (2025). “Sustainable biobased flame-retardant epoxy thermoset derived from renewable phytic acid and itaconic-acid for high-performance rubber wood coatings,” *International Journal of Biological Macromolecules* 315, article 144667. <https://doi.org/10.1016/j.ijbiomac.2025.144667>
- Zhao, H. Y., Ye, Y. D., Zhang, Y. B., Yang, L., Du, W. C., Wang, S. L., and Hou, Z. Y. (2024). “Upcycling of waste polyesters for the development of a circular economy,” *Chemical Communications* 60, 13832-13857. <https://doi.org/10.1039/D4CC04780J>
- Zheng, W. Z., Li, X., Xu, P. Y., Zhang, Z. Y., Wang, P. L., Lu, B., Huang, D., Zhen, Z. C., Ji, J. H., and Wang, G. X. (2024). “Sustainable recycling of the biodegradable polyester poly(butylene succinate) via selective catalytic hydrolysis and repolymerization,” *Resources, Conservation and Recycling* 209, article 107771. <https://doi.org/10.1016/j.resconrec.2024.107771>
- Zheng, W. Z., Li, X., Xie, J., Zhang, Z. Y., Wang, P. L., Huang, D., Ren, Z. L., Ji, J. H., and Wang, G. X. (2024). “Closed-loop recycling of biodegradable poly(butylene adipate-co-terephthalate) based on hydrolysis and repolymerization strategy,” *Journal of Environmental Chemical Engineering* 12, article 114354. <https://doi.org/10.1016/j.jece.2024.114354>
- Zhou, Y. J., Xia, N. N., Zhang, J. L., Li, T. X., Wang, J. M., and Wu, Q. (2025). “Novel reusable wood adhesive comprising disulfide bond-modified polyurethane,” *ACS Sustainable Chemistry & Engineering* 13, 6412-6422. <https://doi.org/10.1021/acssuschemeng.5c02071>
- Zhu, X. X., Wang, H., Liu, B. P., Yang, D. S., Liu, F. S., and Song, X. Y. (2024). “Chemical recycling of polylactic acid to methyl lactate catalyzed by choline chloride/ZnCl<sub>2</sub> deep eutectic solvents,” *Polymer Degradation and Stability* 219, article 110625. <https://doi.org/10.1016/j.polymdegradstab.2023.110625>
- Zuo, H. W., Wen, M. Y., Shi, J. Y., Park, H., Lv, L. X., Ren, Y. N., Zhao, X. F., Du, H. S., Yang, X. J., and Jian, Z. P. (2025). “A robust P-N-Si synergistic flame retardant epoxy coating for wood building material protection,” *Construction and Building Materials* 490, article 142465. <https://doi.org/10.1016/j.conbuildmat.2025.142465>

Article submitted: August 8, 2025; Peer review completed: August 24, 2025; Revised version received: December 12, 2025; Accepted: December 15, 2025; Published: December 26, 2025.

DOI: 10.15376/biores.21.1.Zhang